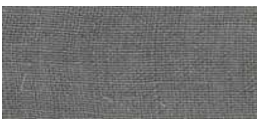


Nuancier fibres cellulosiques

Cellulosic fibers colour chart

		A02 Acétate d'aluminium <i>A02 Aluminium acetate</i>	A05 Lactate de Fer <i>A05 Ferrous Lactate</i>	A03 Oxalate de Titane <i>A03 Titanium Oxalate</i>
		% PDF % WOF 4%	% PDF % WOF 2%	% PDF % WOF 2%
C01	Coréopsis / <i>Coreopsis</i>	4%  Lightfastness : 2,5/8	2%  Lightfastness : 3/8	2%  Lightfastness : 2,5/8
C03	Garance riche / <i>Madder rich</i>	4%  Lightfastness : 3,5/8	2%  Lightfastness : 3,5/8	2%  Lightfastness : 3,5/8
C04	Garance standard / <i>Madder standard</i>	4%  Lightfastness : 3,5/8	2%  Lightfastness : 3,5/8	2%  Lightfastness : 4/8
C05	Genêt / <i>Dyer's broom</i>	4%  Lightfastness : 4/8	2%  Lightfastness : 4/8	2%  Lightfastness : 4/8
C08	Réséda / <i>Weld</i>	4%  Lightfastness : 4/8	2%  Lightfastness : 4/8	2%  Lightfastness : 4/8
C09	Solidage / <i>Goldenrod</i>	4%  Lightfastness : 3/8	2%  Lightfastness : 3/8	2%  Lightfastness : 3/8
C10	Sorgho / <i>Dyer's sorghum</i>	4%  Lightfastness : 2/8	2%  Lightfastness : 2,5/8	2%  Lightfastness : 2/8

C11 Campêche / Logwood	4%  Lightfastness : 3,5/8	2%  Lightfastness : 4/8	2%  Lightfastness : 3/8
C12 2	4%  Lightfastness : 3/8	2%  Lightfastness : 3/8	2%  Lightfastness : 2,5/8
C13 Cochenille / Cochineal	4%  Lightfastness : 1/8	2%  Lightfastness : 1/8	2%  Lightfastness : 1/8
C14 Québracho / Quebracho	4%  Lightfastness : 2/8	2%  Lightfastness : 2/8	2%  Lightfastness : 2/8
C15 Châtaignier / Chestnut	4%  Lightfastness : 5/8	2%  Lightfastness : 3/8	2%  Lightfastness : 3/8
C16 Cachou / Cutch	4%  Lightfastness : 1/8	2%  Lightfastness : 2/8	2%  Lightfastness : 2/8
C18 – A17 Extrait de Noix de Galle de Sumac / Chinese Sumac extract	4%  Lightfastness : 5/8	2%  Lightfastness : 4/8	2%  Lightfastness : 4/8
C20 Myrobalan / Myrobalam	4%  Lightfastness : 6/8	2%  Lightfastness : 5/8	2%  Lightfastness : 5/8
C25 Bourdaine / Alder Buckthorn	4%  Lightfastness : 3/8	2%  Lightfastness : 5/8	2%  Lightfastness : 3,5/8

C31 Extrait de Henné /Hen na extract	4%  Lightfastness : 3/8	2%  Lightfastness : 3,5/8	2%  Lightfastness : 3/8
P10 Indigo tropical / tropical Indigo	0,5%  Lightfasness : 7/8		
	2%  Lightfasness : 7/8		

Les couleurs peuvent varier en fonction de la qualité et les traitements que la fibre utilisée / Colors may vary due to the quality of the fabric and its treatments.

Solidité lumière évaluée sur l'échelle des bleu de 1/8 à 8/8 / Lightfasness evaluated on the bluescale from 1/8 to 8/8
Conditions : Suntest CPS+ 48h - 550W/m² - 50°C